

How to cite this article: Khaledian S, Mohammadi Gh, Abdoli M, Fatahian A, Fatahian A, Fatahian R. Recent advances in implantable 3D-printed scaffolds for repair of spinal cord injury. *Advanced Pharmaceutical Bulletin*, doi: [10.34172/apb.2024.032](https://doi.org/10.34172/apb.2024.032)

Recent advances in implantable 3D-printed scaffolds for repair of spinal cord injury

Salar Khaledian^{1,2}, Ghobad Mohammadi³, Mohadese Abdoli^{4,5}, Arad Fatahian⁶, Arya Fatahian⁶, Reza Fatahian^{2,7*}

¹ Infectious Diseases Research Center, Health Institute, Kermanshah University of Medical Sciences, Kermanshah, Iran.

² Clinical Research Development Center, Taleghani and Imam Ali Hospitals, Kermanshah University of Medical Sciences, Kermanshah, Iran.

³ Pharmaceutical Sciences Research Center, Health Institute, Kermanshah University of Medical Sciences, Kermanshah, Iran

⁴ Department of Nanobiotechnology, Faculty of Innovative Science and Technology, Razi University, Kermanshah, Iran.

⁵ Nano Drug Delivery Research Center, Health Technology Institute, Kermanshah University of Medical Sciences, Kermanshah, Iran

⁶ School of Dentistry, Kermanshah University of Medical Sciences, Kermanshah, Iran

⁷ Department of Neurosurgery, School of Medicine, Kermanshah University of Medical Sciences, Kermanshah, Iran.

* **Reza Fatahian**, Department of Neurosurgery, School of Medicine, Kermanshah University of Medical Sciences, Kermanshah, Iran. **E-mail:** rfatahian@gmail.com

Salar Khaledian : <https://orcid.org/0000-0003-2161-9200>

Reza Fatahian : <https://orcid.org/0000-0001-9164-8483>

Submitted: July 12, 2023

Revised: January 27, 2024

Accepted: March 03, 2024

ePublished:

Abstract

Spinal cord injury (SCI) is an important factor in sensory and motor disorders that affects thousands of people every year. Currently, despite successes in basic science and clinical research, there are few effective methods in the treatment of chronic and acute spinal cord injuries. In the last decade, the use of 3D printed scaffolds in the treatment of SCI had satisfactory and promising results. By providing a microenvironment around the injury site and in combination with growth factors or cells, 3D printed scaffolds help in axon regeneration as well as neural recovery after SCI. Here, we provide an overview of tissue engineering, 3D printing scaffolds, the different polymers used and their characterization methods. This review highlights the recent encouraging applications of 3D printing scaffolds in developing the novel SCI therapy.

Keywords: Hydrogel, polymer-based scaffold, neural protection, function recovery, collagen, silk

1- Introduction

Tissue engineering is a multi-disciplinary science which is used with the aim of creating biological substitutes that can restore, maintain and improve the function of the damaged tissue.¹ The main components of tissue engineering are scaffold, cells and growth factors.² A tissue has a number of structural and mechanical properties to do its function. For this purpose to obtain these conditions in tissue engineering, the cells are cultured inside an artificial structure. These structures are able to mimic and support the structure of three-dimensional fabric structure. This structure is called a scaffold, which is used both *in vivo* and *ex vivo*. In either case, the scaffold is an imitation of living tissue inside the body, allowing the implanted cells to influence the surrounding microenvironment.³ Biological scaffolds are obtained using biocompatible and degradable materials.⁴ As far as possible, the structure of these scaffolds should be as similar to the texture of the planting area. In this way, the reconstruction and improvement of the damaged tissue will increase in quality and quantity. In addition to high mechanical strength, the scaffold structure must have good porosity in order to proper cell nutrition, disposal of cellular lesions to the outside of the scaffold, formation an extracellular matrix, and angiogenesis.⁵ Fig 1 shows a general approach to tissue engineering.

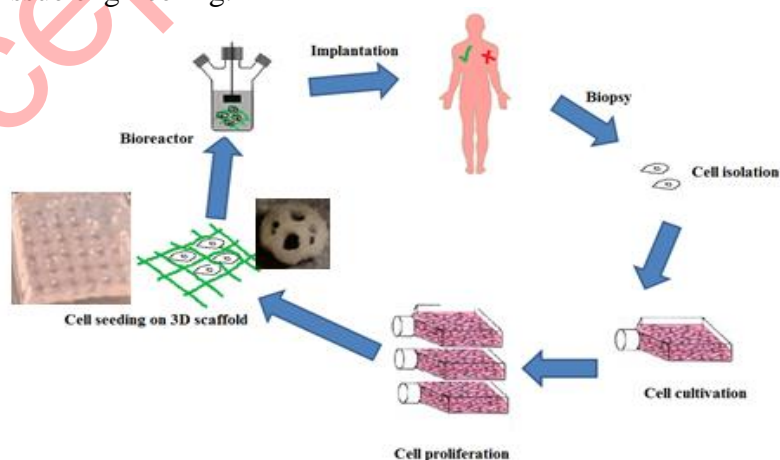


Fig 1. The steps of the tissue engineering process. First, a biopsy of liquid or solid tissue is performed. The cells are isolated using centrifugation or apheresis and then cultured and proliferated. After these cells are implanted in

an artificial structure that is similar to the extracellular matrix and can support the formation of 3D tissue. Finally, after passing through the bioreactor stage (simulation a physiological environment), tissue is implanted inside the living body.

Over the past decade, many advances in tissue engineering have been made to repair damaged tissues, including bone, cartilage, skin, cardiac, vascular, liver and nerve tissue.⁶ Spinal cord injuries (SCI) are relatively common clinical problems that often lead to permanent sensory and motor disabilities in patients. The number of publications about SCI in the last two decades, shows considerable importance of this subject (Fig. 2). In the United States, more than 500,000 people suffer from spinal cord injuries, which result in significant psychological and economic costs.⁷ Common treatment strategies for SCI include drug treatment (minocycline, ketorolac, etc.), non-drug treatment (decompression, stabilization, etc) and cell transplantation. The prescription of each of these treatment methods depends on the progressive stage of the SCI.⁸ However, scientists and researchers have made extensive efforts to find new and more effective ways to treat this disease. A large number of *in vitro* studies examine cells in a two-dimensional (2D) environment, while in physiological situations in the human body, cells grow in a three-dimensional (3D) environment.⁹ Obviously, in a 2D environment; metabolism, gene expression, role of extracellular matrix (ECM) proteins, and morphology of cultured cells are differ with that occurs under physiological and *in vivo* conditions. As *in vitro* studies become more and more similar to *in vivo* conditions, the construction of three-dimensional cellular networks was developed to replace the damaged tissue.¹⁰ Combining 3D printing technology with tissue engineering, a new solution was introduced to improve and treat SCI. Scaffolds obtained by classical methods such as particulate leaching, organic foam impregnation, etc., usually have uncontrolled pore size, inadequate high mechanical strength, poor pore geometry and connections. In contrast, scaffolds produced with 3D printers their mechanical properties controlled by pore structure, and their biological activity and degradation are regulated by chemical composition.¹¹ Over the past decade, research on 3D printing has accelerated significantly. Therefore, the purpose of this study is to review the applications of 3D printed scaffold in SCI repair.

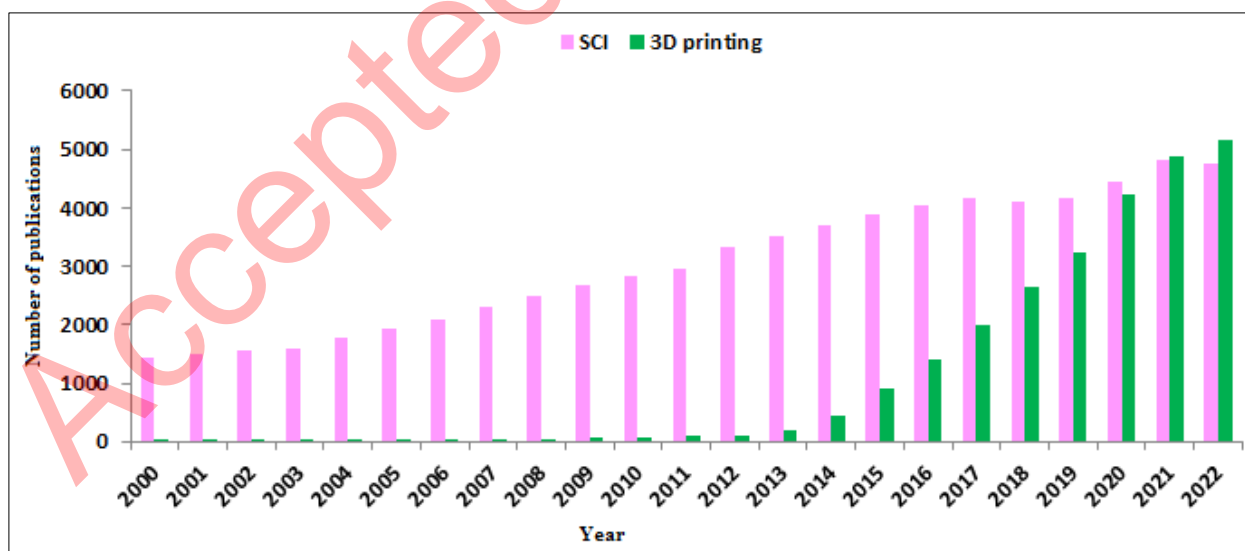


Fig 2. Publication number related to SCI and 3D printing in 2000-2022 years (PubMed* database). In the past decade, the use of 3D printed scaffold in the treatment of SCI has increased significantly.

2- 3D printed scaffolds: definitions, types of polymers, synthesis routs, advantages and disadvantages, and so on . . .

The 3D printing scaffolds are structures with controlled pore size and interconnectivity that are capable of supporting cell growth and tissue formation.¹² In order to be more efficient, these scaffolds must have critical features such as biocompatibility, biodegradability, mechanical properties and etc..¹³ The first criterion that is of great importance for any tissue engineering scaffold is biocompatibility. Cell binding, migration and proliferation are directly affected by this factor.¹⁴ Proper biodegradability is another essential feature of scaffolds that in addition to adequate mechanical support prevents the inflammatory response to external scaffold materials. Also, porous structures should facilitate the release of nutrients and metabolic wastes, which in turn increases the metabolic activity of cells. Moreover, the mechanical strength of a scaffold must be sufficient to support the structures in the weight-bearing tissues before the newly formed tissue is synthesized.^{15,16} Eventually, the biomaterials used to prepare tissue engineering scaffolds should be readily available and have the desired fabricability, so that the scaffold produced is compatible with various tissue defects in patients.¹³ Porosity, pore size, and interconnected pore structure are important factors in 3D printed scaffolds that promote cell survival and enhancing tissue growth.¹⁷ There are two types of porosity including open (also called interconnected) and closed. In open porosity, the pores are connected like channels, while in closed porosity; the pores are separate and not connected.¹⁸ Interconnected porosity is very important in tissue engineering and plays an important role in cell nutrition, proliferation, migration and formation of new tissues.¹⁹ Porosity, in addition to supporting cell migration to the scaffold, improves the available surface for cell attachment to the scaffold and its interaction with the surrounding tissues.¹³ Several studies have shown that scaffolds with sufficient porosity are able to stimulate tissue growth while retaining their mechanical properties.^{11,20} Liu *et al.* fabricated 3D printed scaffolds by collagen and mixture of collagen/chitosan. They compared in this study the microstructures of these scaffolds were compared and a higher total open porosity in the collagen/chitosan case was obtained, which led to improve mechanical strength and facilitate the diffusion of nutrient solution and tissue formation.²⁰ In addition, 3D printed scaffolds should have good electrical conductivity to improve the therapeutic effect of SCI. Conductive scaffolds significantly improve the neural differentiation of cells and recovery of motor function.²¹ Finally, the biomaterials must be available and have the desired manufacturing capability to prepare scaffolds with different shapes and suitable for different patients.¹³ Various polymers either naturally derived or synthetic are used for 3D printed scaffolds (Fig. 3). In the following, each of these polymers will be discussed briefly.

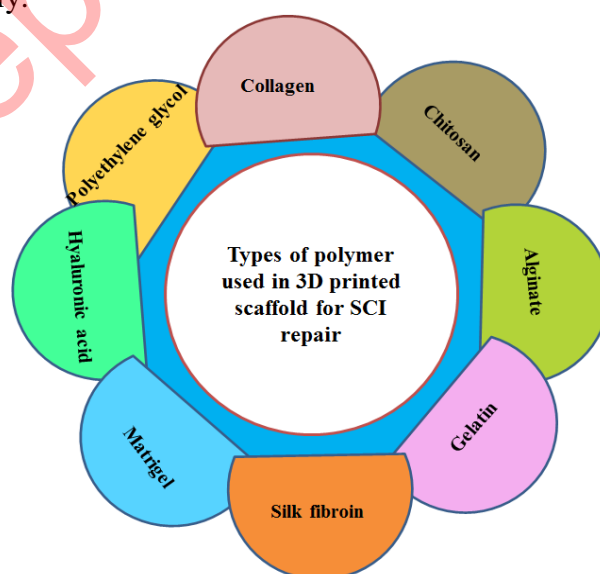


Fig. 3. Types of polymer used in the preparation of 3D printed scaffold.

2-1 Collagen

Collagen is one of the main proteins of the extracellular matrix, which consists of three alpha polypeptide chains with one or more secondary structures forming a triple helix.^{22,23} The triple helix is usually composed of three polypeptide chains that consist of repeated amino acid units including glycine, proline and 4-hydroxyproline.²⁴ Due to hydrogen bonds, the fibrils formed from these triple helices have high strength and good flexibility and can be connected together, which improves the mechanical properties of 3D printed scaffolds.²⁵ The researches on SCI showed that this compound acts as a bridge in the area of the injury and leads to the formation of blood vessels followed by axonal growth.¹¹ The results of previous studies in rat models with completely transected spinal cords show that collagen plays a role in reducing lesion area, supporting cell migration, directing orderly regeneration of nerve fibers, and direct axon elongation, all of which improve nerve function.^{26,27} In addition, collagen can act as a delivery carrier for trophic factors and cells to the injury site and form a suitable microenvironment around the injury.²⁸ Despite the weak immunogenicity and good biocompatibility of collagen, this polymer faces limitations such as low mechanical properties and high speed of degradation.²⁹ One of the strategies presented to increase the mechanical strength and also reduce the rate of degradation is the use of collagen aggregate (extracted from bovine tendon) in the preparation of scaffolds. The results of a study showed that scaffolds made from collagen aggregate increase mechanical strength up to 11 times compared to scaffolds made from collagen molecules.³⁰ Chemical modification of collagen through carbodiimide is another way to increase mechanical strength and reduce the rate of degradation by enzymes. Creating bonds between amino groups and free carboxyl groups of collagen fibers improves its mechanical properties.³¹ In this regard, Stiglic et al. reported that the 3D printed scaffold prepared from collagen, carboxymethyl cellulose and nanofibrillated cellulose has high mechanical stability for tissue engineering applications.³²

2-2 Chitosan

Chitosan is a biological polymer that is obtained from chitin as a result of the deacetylation process.³³ Chitosan, having characteristics such as biodegradability, low toxicity, non-antigenicity, non-hemolysis, and good plasticity, is often used in nerve repair to improve function after SCI.^{34,35} In addition, chitosan has significant neuroprotective properties, maintaining cell membrane integrity and preventing lipid peroxidation during SCI treatment.³⁶ Adding chitosan to collagen delays its decomposition and also increases the mechanical properties of the scaffold. However, the degradation time of chitosan is long and it is not suitable for spinal cord transplantation. Hence, a mixture of both substances can overcome the limitations of a pure substance.

2-3 Alginate

Alginate is a linear polysaccharide extracted from seaweed that has good stability, solubility, viscosity, and biodegradability.³⁷ It is usually used as sodium salt. By adding multivalent cations such as Ca^{2+} and Mg^{2+} , which creates ionic bonds between the carboxyl groups of polymer chains, mechanically stable hydrogels were produced.³⁸ This key feature can be used especially in tissue engineering and regenerative medicine.³⁹ In this regard, various researches have shown that alginate meliorate axon regeneration without causing inflammatory and allergic reactions.⁴⁰

2-4 Gelatin

Gelatin with a molecular weight between 15-400 kDa is a very biocompatible and biodegradable protein-based polymer and has many applications in the fields of drug delivery, gene therapy, wound healing, regenerative medicine, and tissue engineering.⁴¹ This polymer obtained from the collagen through the hydrolysis of natural triple-helix structure of collagen to single-strand molecules.⁴² Compared to collagen, gelatin is less immunogenic and have an important role in the promoting cell adhesion, migration, differentiation and proliferation due

to RGD motif.⁴³ Furthermore, the combination of gelatin with alginate in 3D printed scaffold improve the mechanical properties and reduce the rate of degradation.⁴⁴

2-5 Silk fibroin

Silk fibroin (SF) with molecular weight (200–350 kDa or more) is another natural protein that is produced by different kind of insects and spiders.^{45,46} The most important advantage of SF compared to other natural biopolymers is having excellent mechanical properties. Other advantages of SF include excellent biocompatibility, water-based processing, biodegradability, and the presence of chemical groups for functional changes.⁴⁷ This polymer was used in the soft tissue engineering and reconstruction as a biomaterial.^{47,48} Combination of SF with collagen for preparation of 3D printed scaffold can compensate some limitation of collagen, such as poor mechanical strength, low manipulability and fast degradation.^{49,50}

2-6 Matrigel

MatrigelTM is a mixture of basement membrane matrix that have been extracted from Englebreth-Holm-Swarm (EHS) tumors in mice.⁵¹ This protein mixture mostly consisting of laminin, collagen type IV, enlactin and various growth factors (GFs).^{52,53} scaffolds prepared from the matrigel are mainly used for cell differentiation, tissue vasculature and angiogenesis.^{54,55} Due to mimicking the extracellular matrix components, matrigel could promote cell adhesion on the scaffold.^{56,57} however it has a poor mechanical properties and for application in 3D printing should be combined with another polymers such as alginate, chitosan and etc..⁵⁸

2-7 Hyaluronic acid

In two last decades, hyaluronic acid (HA) as a long and natural linear polysaccharide has attracted a lot of attention in the biomedical fields specifically in wound healing and tissue engineering.^{59,60} HA is a mixture of two disaccharides including D-glucuronic and N-acetyl-D-glucosamine and have a critical role in different biological processes like a tissue hydration, nutrient diffusion, proteoglycan organization and cell differentiation.⁶¹ The molecular weight and concentration of HA ranging between 120-2500 kDa and 0.1-4% w/v has been reported respectively for 3D printing application.⁶²

2-8 Polyethylene glycol

Polyethylene glycol (PEG), a synthetic hydrophilic polymer with biocompatible and non-immunogenic properties that has been widely used in tissue engineering and to improve the wettability of scaffolds.^{63,64} It has been reported that PEG can reseal axonal membranes following SCI. Furthermore, PEG may directly lead to a significant reduction of mitochondrial-derived oxidative stress and prevent its effects on intracellular components.⁶⁵ However, the use of PEG in the fabrication of 3D printing scaffolds has some limitations. The obtained scaffolds do not provide a suitable biological environment for cell proliferation. In addition, cell survival depends on photocrosslinking time, light intensity and photoinitiator.⁶⁶

2-9 Types of 3D bioprinting technology in SCI repair

According to the previous research, various 3D printing techniques have been used for treatment of SCI, each of them will be briefly discussed below. 3D bioprinters are classified into 4 categories including extrusion-based, inkjet-based, laser-assisted, and stereolithography-based bioprinting,⁶⁷⁻⁶⁹ although other classifications have been reported.⁷⁰

Among the mentioned systems, extrusion based system is mostly used. In this method pneumatic or mechanical (piston or screw) dispensing systems is used to extrude a continuous bioink stream which leads to excellent structural integrity of the scaffold.^{71,72} This technic can

be divided to two category including syringe-based microextrusion or microfluidic extrusion.⁷³ In the mentioned system, at first the cells and bio-ink are mixed and then the biomaterials are dispensed through nozzles or needles.⁷¹ The major advantage of this process are easy application, ability to print different kinds of materials and fabrication of cell density with high values.^{74,75} However, low printing resolution,⁷⁶ low viscosity bioinks⁷⁷ and optimization of parameters like as component concentration, pressure and diameter of the nozzle are among the limitations of this method.⁷⁸

Inkjet based bioprinting is an affordable method that using a diversity of energy sources produce bioink droplets.⁷⁴ Therefore, there are two types of inkjet printers including thermal and piezoelectric. In these methods by apply the temperature and piezoelectric actuator, air-piezoelectric-pressure pulses were produced and lead to ejection of droplets from the nozzle.⁶⁹ Among the advantages of these methods can be mentioned high printing speed, high resolution (between 20 and 100 μm), and good biocompatibility.^{76,79} But, the blocking of nozzles and the need to use low-viscosity bioinks to solve this problem are among the limitations of these methods, which, by imposing thermal or mechanical pressure, ultimately lead to a decrease in cell viability.^{80,81}

Laser-assisted bioprinting (LAB) is another promising technology for fabrication of 3D scaffold.⁸² In this method, a variety of bioinks with different viscosity have used without any effects on cell viability and function.^{83,84} In this system, with pressures generated by laser beam, bioink droplets were eject onto a collector substrate which contains culture media to support cell growth.⁷⁵ High printing resolution ($\approx 10 \mu\text{m}$) and high cell density ($\sim 108 \text{ cells/mL}$) are among the advantages of this method.⁸⁵ On the other hand, contaminations with metallic residue reported as a disadvantage of the mentioned system.⁸⁶

In the stereolithography-based bioprinting, ultraviolet (UV) laser are used for printing of light sensitive substances that polymerize to soft substrate materials.⁸⁷ This method has a high printing resolution (5-50 μm) which depends on various factors including laser power, exposure time, size of the laser spot, and value of light wavelength.^{88,89} However, the mentioned system has a limitations such as slow printing time and restriction in type of bioinks for 3D printing applications.^{90,91}

3- 3D printed scaffold characterizations: porosity, stability, biodegradability, compatibility (hemo/Cytocompatibility) and so on . . .

Characterization of 3D printed scaffolds are performed by various analysis including scanning electron microscopy–energy dispersive X-ray spectroscopy (SEM–EDS), rheometry, powder X-ray diffraction (PXRD), Fourier-transform infrared spectroscopy (FT-IR), compression tests and etc. After sample drying and sputter-coating with gold, the morphology of 3D printed scaffold is observed by SEM or FE-SEM. Rheometer is used for measure the rheological properties of hydrogels. Two analyzers are used to investigate the mechanical properties of 3D printed scaffolds and compare them with native spinal cord tissue. Atomic force microscopy (AFM) analysis is used to examine the local mechanics of gray and white matter. Mechanical tester is also used to measure the elastic modulus of 3D printed scaffolds. Finally, the prepared values for native spinal cord tissue and 3D printed scaffolds are compared.⁹² In addition, FTIR spectroscopy is used to confirm the presence (or absence) of functional groups in the scaffold and XRD analysis gives complete structural information about that. Furthermore, the differential scanning calorimetry (DSC) are performed for measuring the thermal stability of fabricated scaffold. For swelling ratio measurement, after immersion the amount of scaffold in phosphate buffer saline (PBS), the weight of the swollen sample is measured.⁹³ The swelling ratio (SR) is calculated through a formula below:

$$SR = \frac{W_s - W_d}{W_d} \quad (1)$$

W_s = weights of the swollen sample and W_d = dry weight of the sample

In order to measuring the water absorption ratio, the dried scaffold is swelled in PBS for 1-7 days and after removal free water of the surface, the weight of the sample is measured.¹¹ The amount of water absorption (WA) is calculated according to the below equation:

$$WA = \frac{M_t - M_0}{M_0} \cdot 100\% \quad (2)$$

M_t = weights of the swollen sample and M_0 = dry weight of the sample

For porosity ratio, the scaffold is immersed into absolute ethyl alcohol.¹¹ Porosity ratio (P) is calculated by following formula:

$$P = \frac{V_0 - V_2}{V_1 - V_2} \cdot 100\% \quad (3)$$

V_0 = volume of alcohol in the beginning, V_1 = volume of alcohol after negative pressure degassing and V_2 = volume of the residual alcohol after taken out the scaffold

For investigation of *in vitro* degradability, the scaffold is incubated in PBS that containing various enzyme such as collagenase, gelatinase, hyaluronidase and among other. Then changes in the wet weight of the scaffold over time is measured.⁹⁴ For *in vivo* degradability, after a longitudinal incision in the dorsal area of the rat, the 3D printed scaffold is implanted into the cystic space.⁵⁰ After 7, 14, 21 and 28 days, the scaffold is removed and degradation rate (D) is calculated using below equation:

$$D = \frac{W_0 - W_T}{W_0} \cdot 100\% \quad (4)$$

W_0 = quality of materials in the beginning and W_T = quality of the residual materials after degrading

Finally, cell compatibility of 3D printed scaffold is evaluated by MTT assay. Also, after 3D bioprinting process, cell viability and cell proliferation are assessed by LIVE/DEAD Viability/Cytotoxicity Kit and MTT method.

4- 3D printed scaffold applications in spinal cord injury repair

Various 3D printed scaffold for SCI repair has been reported in the recent years. In this regards, Li and co-workers designed an *in vitro* 3D printed sodium alginate-matrigel scaffold to promote the differentiation and growth of ectomesenchymal stem cells (EMSCs). Based on the *in vitro* results, in addition to better neural differentiation efficiency compared to 2D culture, the cell survival rate on the 3D printed scaffold was more than 88%.⁵⁸ In another study, Joung *et al.* produced 3D printed scaffold based on matrigel/gelatin/ gelma with microextrusion-based method. Their results showed that the sNPCs and OPCs were distributed in specific channels (Fig 4A) and cells were alive for 3 d after printing in all three layers (Fig 4B) which indicates that the this 3D printed scaffolds are neurocompatible for both cell types.⁹⁵

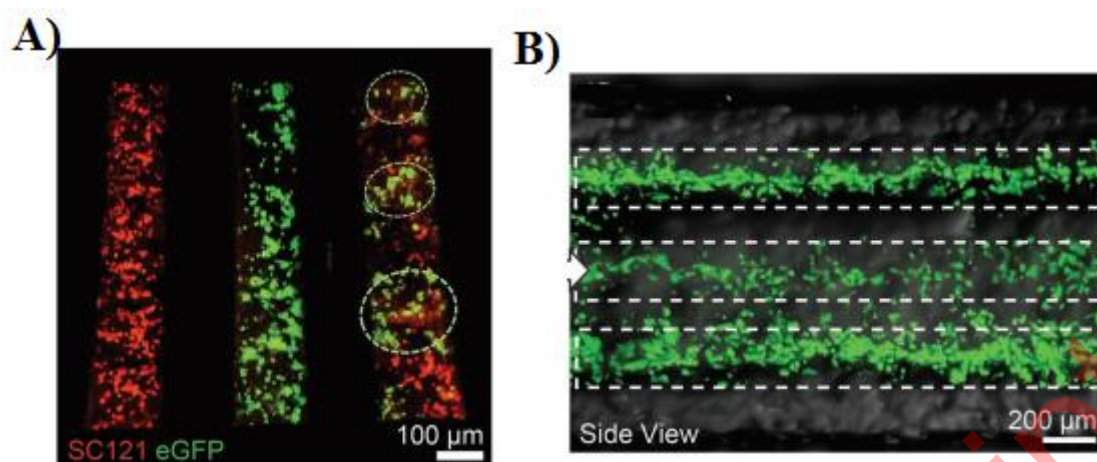


Fig. 4. A) Distribution of cell types in specific channels: sNPCs only (left), OPCs only (middle), and sNPCs and OPCs (right). B) longitudinal side view of fluorescence images of a 3D printed scaffold.⁹⁵

Lio and colleagues fabricated a 3D printed sodium alginate/gelatin scaffold combined with neural stem cells (NSCs) and oligodendrocytes (OLGs) and investigated their effects on nerve regeneration after SCI.⁴⁴ Based on their results, after 3 and 5 days the mean cell survival was about 83% and 76%. The prepared scaffolds (volume about $3 \times 2 \times 3 \text{ mm}^3$ containing 2×10^4 cell) implanted into the transected rat spinal cord for 8 weeks. The *in vivo* results showed that the 3D printed scaffold loaded with both cells compared to other groups (SCI and Scaffold) obviously ameliorated neural generation, axon growth, and locomotor functional recovery (Fig. 5).

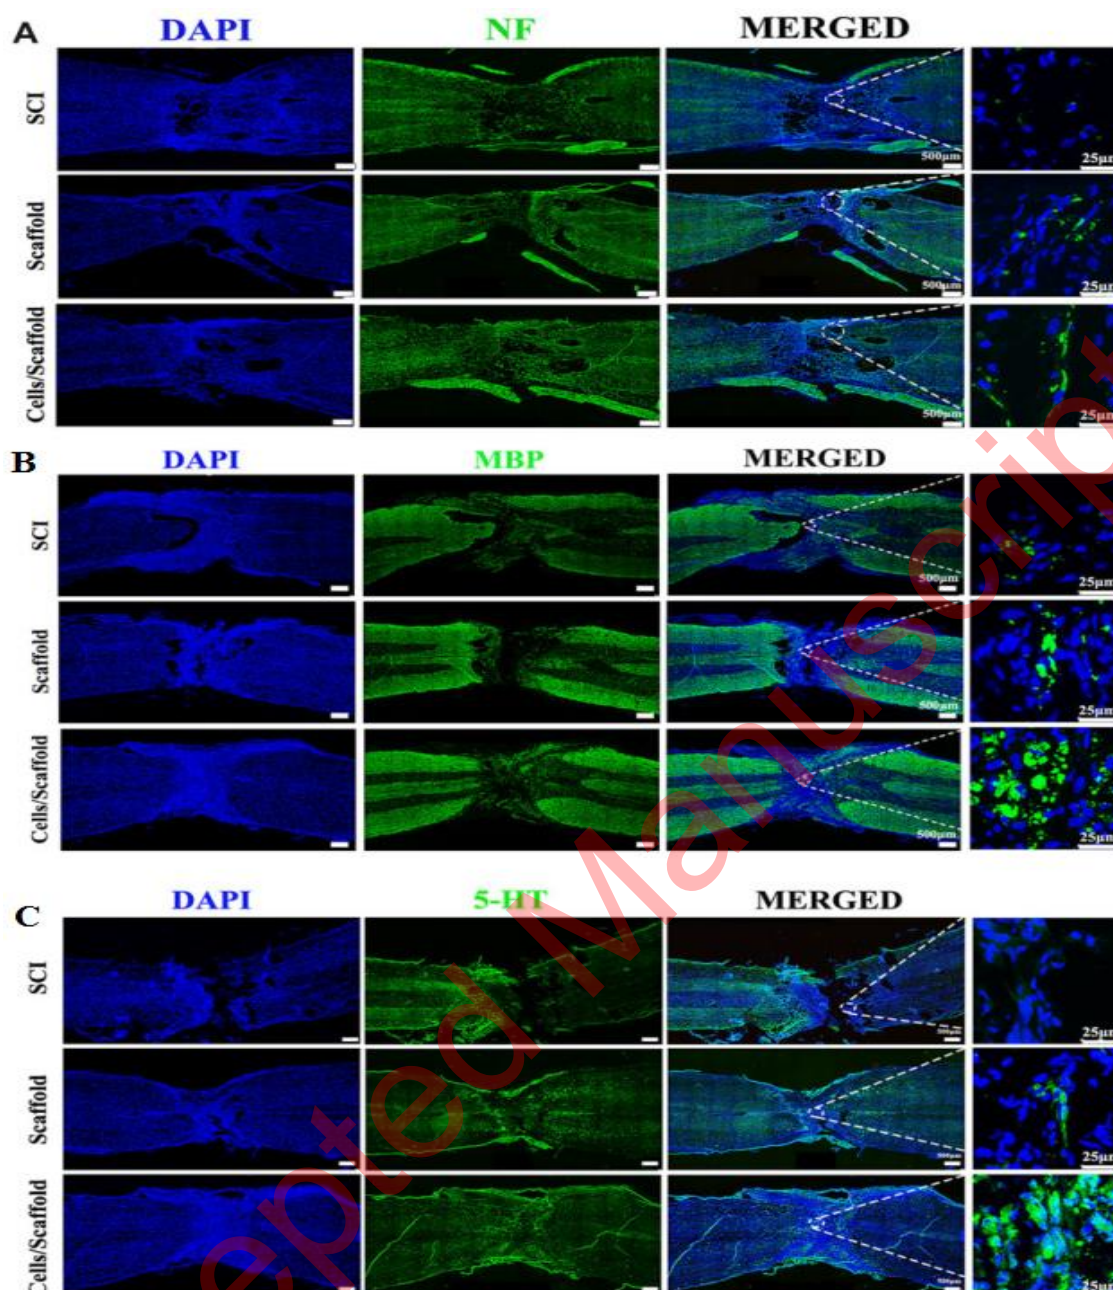


Fig. 5. 3D bioprinting scaffold with NSCs and OLGs promoted myelinization and regeneration of axons. Immunofluorescence staining against NF (A), MBP (B) and 5-HT (C).⁴⁴

Liu *et al.*⁹⁶ produced NSC-laden scaffolds using microextrusion-based 3D printing system. They announced that the cell survival rate was more than 95%. In addition, their result showed that 3D printed scaffold (volume about $4 \times 2 \times 2 \text{ mm}^3$ containing 3×10^5 cell) providing a good microenvironment for cell growth and neural differentiation. Furthermore, after implantation for 12 weeks, the locomotor function in rat model was improved by promoting the axon regeneration and reduced glial scar deposition. In another study, Lio and co-worker constructed a BDNF/collagen/chitosan scaffold using a extrusion 3D printer.²⁰ Their results showed that combination of collagen and chitosan leads to improvement of physicochemical properties of scaffold including mechanical strength, elastic modulus, porosity ratio and etc. In addition, NSCs or HUCMSCs grew fine on this scaffold, which indicating a good cytocompatibility of scaffold. Based on the in vivo experiments, implantation of 3D-CC-BDNF for 8 weeks ameliorated locomotor function after SCI (Fig 6A). Furthermore, by transplantation of the

mentioned scaffold after SCI the regeneration of nerve fibers tracts were promoted (Fig 6B). Also, with the implantation of prepared scaffold a) the gap at the site of injury is filled, b) the regeneration of the nerve fiber is facilitated and c) the creation of synaptic connections is accelerated.

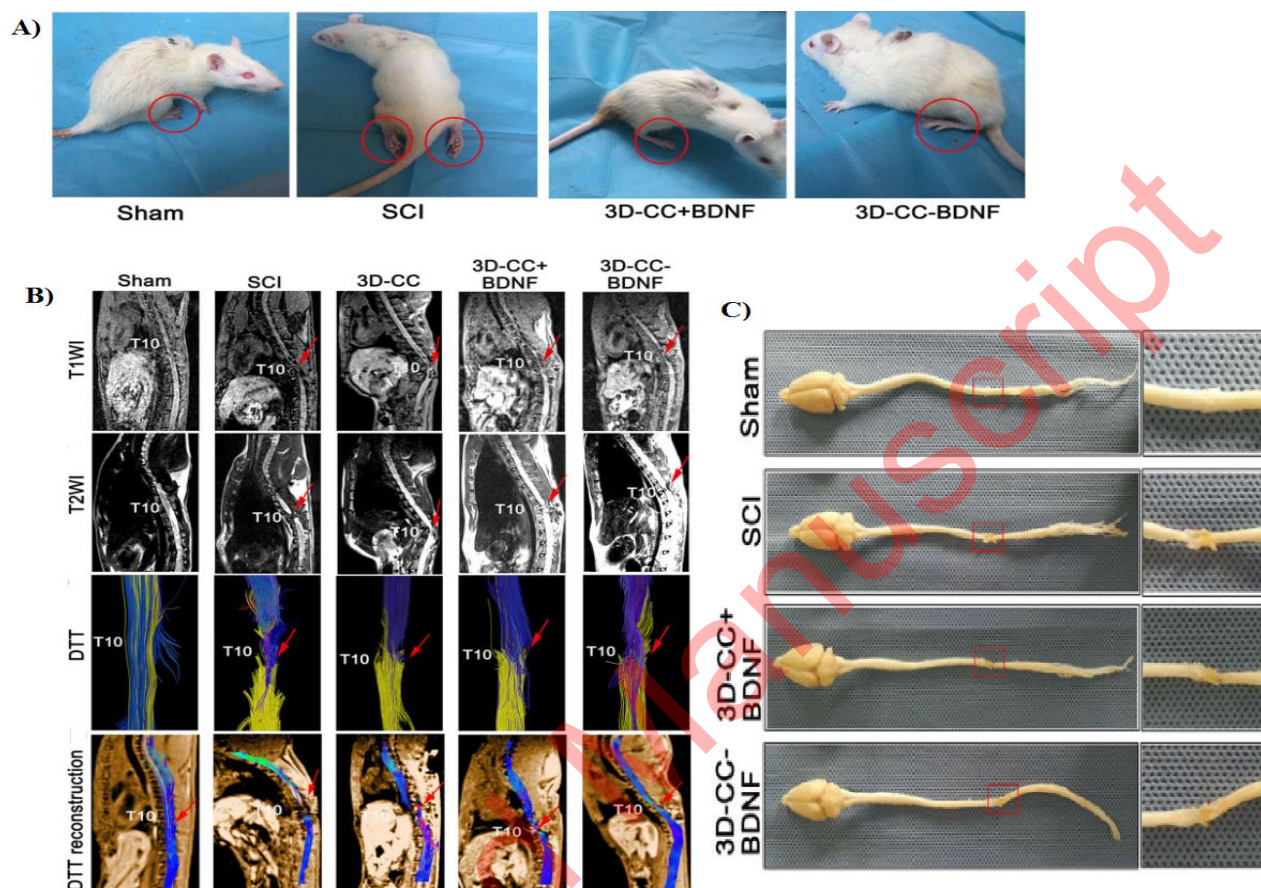


Fig. 6. A) Typical picture of rats in the four groups at 8 week after the operation. B) Magnetic resonance imaging (MRI) and diffusion tensor imaging (DTI) at 8 weeks after SCI. C) Macroscopic histology images of spinal cord.²⁰

Sun and colleagues in 2019 produced a 3D printed collagen/chitosan (3D-C/C) scaffold for treatment of SCI.¹¹ In this study, 3D-C/C scaffold is implanted into the T8 complete transection SCI rat model. Their results showed that compared to other group (SCI or C/C group), 3D-C/C scaffold implantation leads to improving the locomotor function in SCI rat. Based on MRI-DTI images, using this scaffold and compared with SCI group the spinal cord fibers around the lesion site were significant elevated (Fig 7A). Also, they stated that after 8 weeks implantation of 3D-C/C scaffold the scar and cavity production were decreased and the regeneration of nerve fibers were improved (Fig 7B).

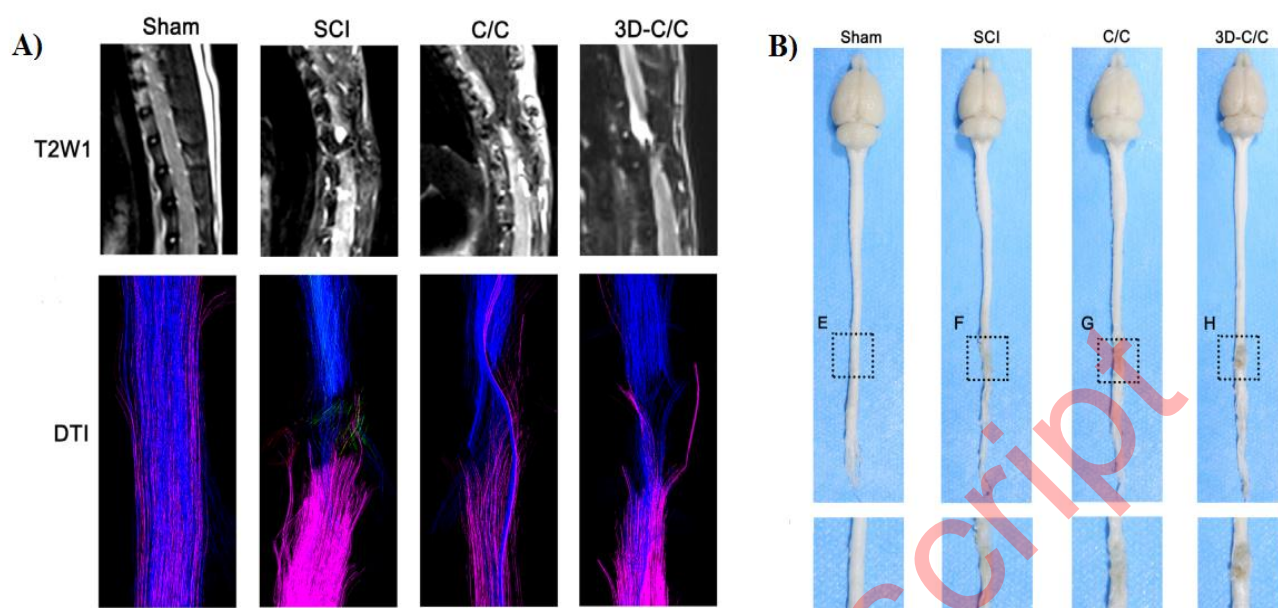


Fig. 7. A) MRI-DTI evaluating the recovery of white matter fiber after SCI. B) The spinal cord and brain were retrieved after perfusion of 4% formaldehyde at 8 weeks post-surgery.¹¹

Li *et al.* developed a 3D printed collagen/silk fibroin (3D-C/SF) scaffold for the treatment of SCI.⁵⁰ In this study, the completely transected SCI rats were implanted with 3D-C/SF scaffold and their functional recovery was evaluated after 8 weeks. Their results showed that this 3D printed scaffold promoted the locomotor function after SCI. Also, based on the MRI results in the 3D-C/SF group compared to SCI and C/SF group the axonal regeneration was significantly improved (Fig 8A). In addition, histological analysis showed that lesions and disordered structures were fewer in 3D-C/SF scaffold compared to other groups (Fig 8B).

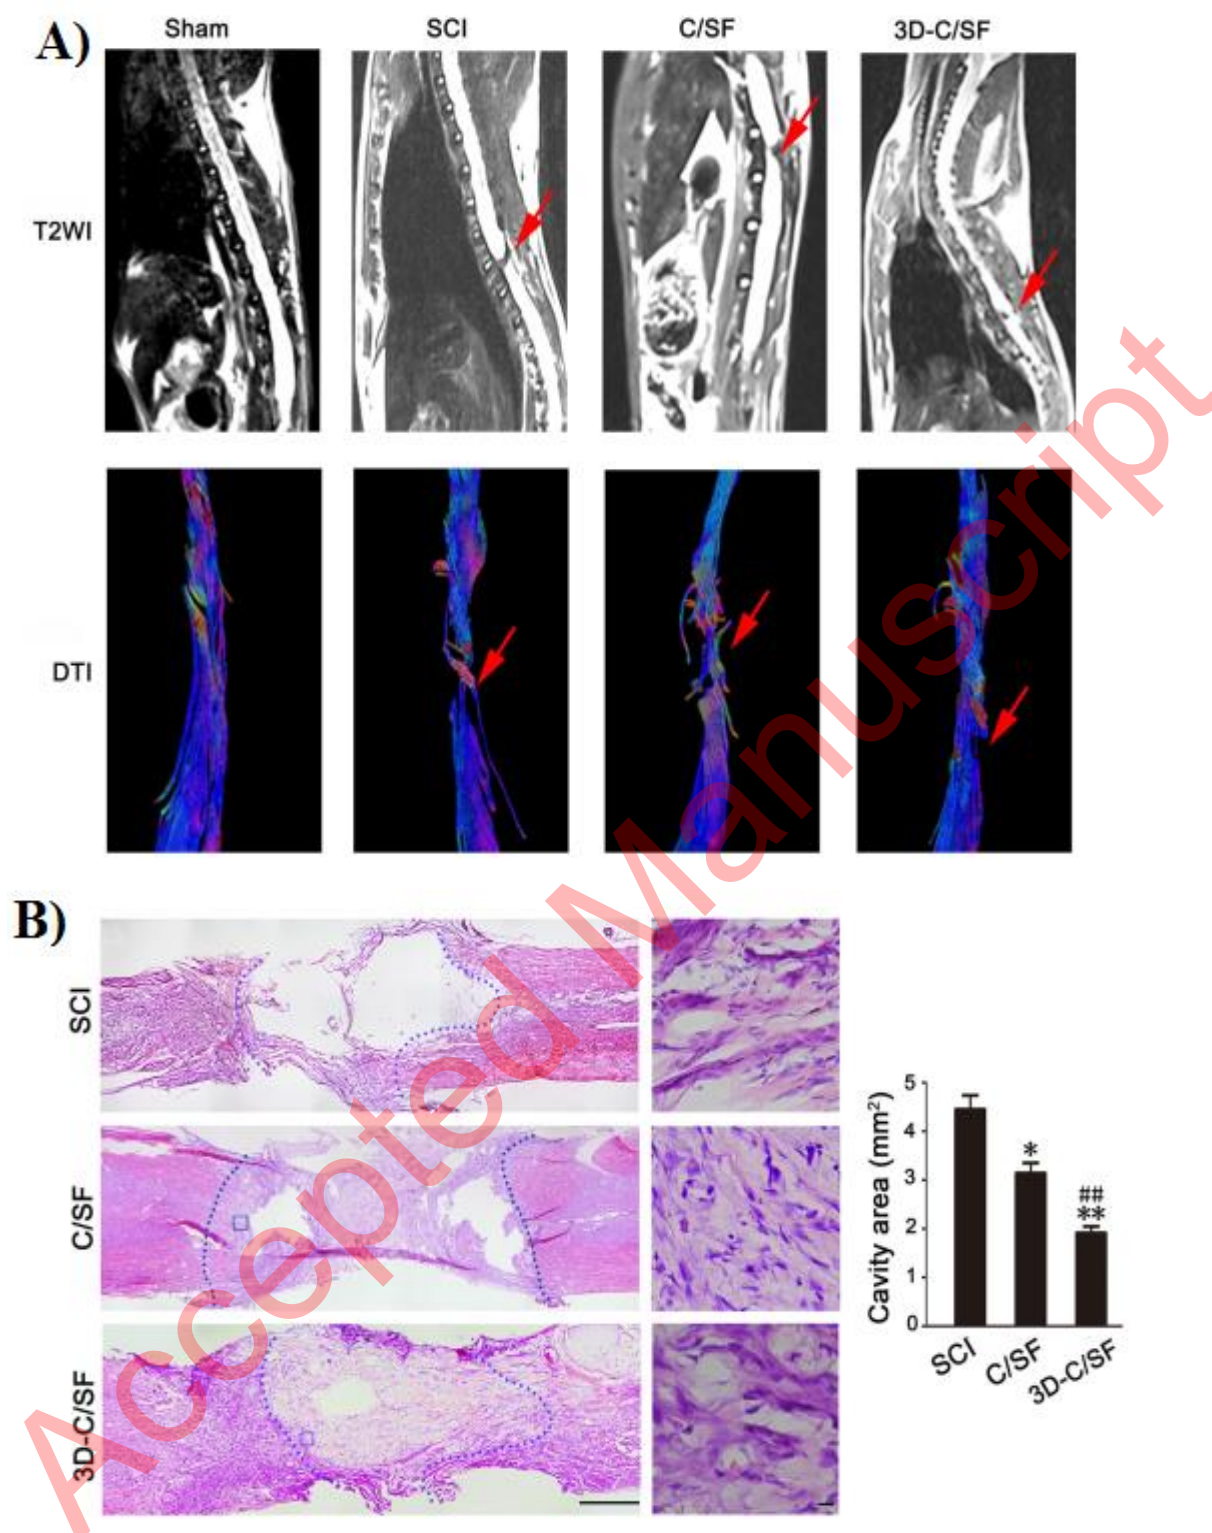


Fig. 8. A) MRI images of spinal cord in each group at 8 weeks after implantation. B) HE staining at 8 weeks post injury.⁵⁰

In another work, Jiang and co-workers fabricated a 3D printed collagen/silk fibroin scaffold loaded with neural stem cells for nerve regeneration after SCI.⁹⁷ Based on the results, the NSCs exhibited strong proliferation and differentiation ability. In addition, in the 3D-CF + NSCs groups the locomotor function of SCI rats were improved at 8 weeks after surgery. Also, the cavity in the injury site was filled with 3D printed scaffold and regeneration of nerve fibers

were enhanced. Chen and colleagues in 2022 developed a 3D printed collagen/silk fibroin scaffolds combined with secretome of human umbilical mesenchymal stem cells (3D-C/S+ST).⁴⁹ In comparison to 3D-C/S scaffold, the 3D-C/S+ST scaffold showed a good cytocompatibility and was better for NSCs growth. Based on their results 8 weeks after surgery, the locomotor function as well as the hindlimb walking ability of 3D-C/S+ST group were notably improved (Fig 9A). In addition, MRI and DTI image indicates that after implantation of 3D-C/S+ST scaffold into the T10 complete transection SCI rat model, the nerve fibers tracts regeneration was enhanced (Fig 9B). Also, the implanted scaffold significantly decreased cavity formation, improve nerve fiber regeneration and remyelination at the injury site (Fig 9C).

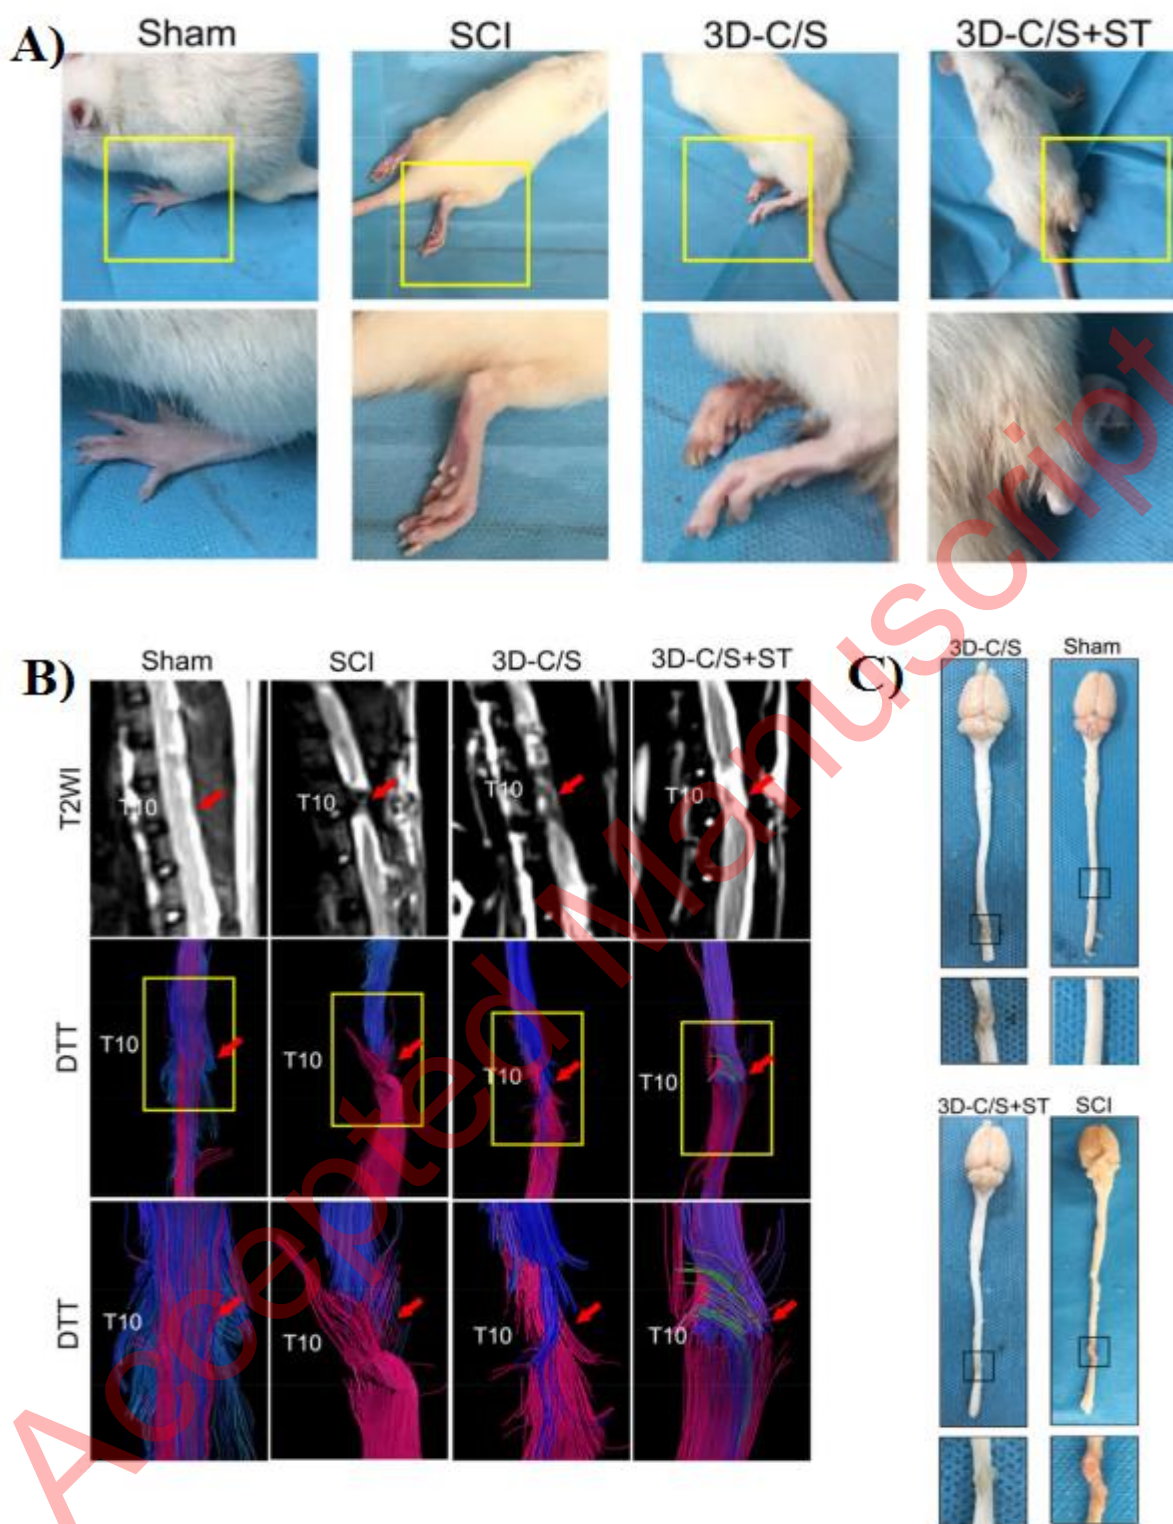


Fig. 9. A) Representative gait records of walking gaits of hindlimbs of rats in each group at 8 week after surgery. B) MRI and DTI images at 8 weeks after surgery. C) Representative macrograph of spinal cord at 8 weeks post-surgery.⁴⁹

Koffler *et al.* in 2019 fabricated a 3D PEG–GelMA printed scaffolds loaded with neural progenitor cells (NPCs) for SCI repair.⁷ In this study the prepared scaffold implanted into SCI rats. Based on their results, after 6 month, in every grafted animal the NPC cells survived and completely filled the channels of the scaffold. Furthermore, in vivo results indicates that 3D

printed scaffolds combined with NPCs significantly enhance host axonal regeneration into the lesion. Based on the anatomical analysis, the scaffolds maintained their 3D architecture after 6 months. In addition, the functional recovery of animal that received scaffolds loaded with NPCs were improved compared to animals with empty scaffolds.

In another study, the T3 complete transection SCI rat models were implanted with 3D PEG-GelMA scaffold loaded with NPCs and compared with 3D-printed scaffolding made of hyaluronic acid, traditional agarose scaffolding, or NPCs without a scaffold. Their results showed that after 4 weeks all NPCs survived and axon regeneration and myelination improved.⁹⁸

Yang *et al.* produced a 3D printing scaffold containing NSCs for long-distance SCI regeneration.⁹⁴ Their results showed that the viability of cells after 7 day of printing were more than 94%. In addition, the implantation of scaffold in SCI rat model significantly enhanced nerve and myelin regeneration. Also, this system reconstruct a functional network at the injury site, which was the essential situation for functional recovery.

Gao and co-worker developed a 3D printed conductive hydrogels based on GelMA, HAMA, and PEDOT:LS.²¹ Based on their results, the NSCs viability was more than 90%. *In vitro* results show that the prepared scaffolds significantly promoted neuronal differentiation of NSCs. Also, implantation of prepared 3D printed scaffold leads to improving the locomotor function in SCI rat model (Fig 10). Furthermore, the use of these 3D printed scaffolds reduces glial scar deposition, and promotes the regeneration of nerve axons and myelination in the injury site.



Fig. 10. Typical hindlimbs-spreading status of SCI rats on week 8 post-surgery.²¹

Concluding and future perspective

Currently, the treatment of SCI is considered as an important and fundamental challenge in the world. The obvious reason for the lack of treatment is the poor recovery ability of the central

nervous system (CNS). Various chemical and physical factors are effective in preventing the reconstruction of SCI. Inhibitory chemical barriers at the site of SCI include inflammatory factors, free radicals of oxygen, inhibitory amino acids and neurotransmitters, which easily lead to toxic reactions and exacerbation of local edema, resulting in insufficient blood supply and accumulation of neurotrophic substances. Furthermore, the loss of spinal cord tissue and the formation of hypertrophic glial scar are physical obstacles to the regeneration of axons. Many evidences show that the implant of biomaterials is a successful strategy for neurological treatment after SCI. Scaffolds that are prepared by traditional methods such as particulate leaching, organic foam impregnation, pore-forming agent, freeze-drying, etc. have an amorphous and irregular structure and are not suitable for axon regeneration at the lesion site. Scaffolds prepared with 3D printing technology have a several advantage including:

- A) Good biodegradability (more than 50% of the scaffolds are decomposed after 8 weeks of implantation) without significant inflammatory reaction
- B) Having a typical shear-thinning behavior to protect cells from shear force damage during the printing process
- C) Excellent cell compatibility and cell adhesion ability
- D) Having a porous structure that can increase oxygen, nutrition, and waste transfer
- E) Improve the cell-matter and cell-cell interactions, tissue integration and rapid vascularization
- F) High potential in regenerating axons by improving the chemical microenvironment and physical barriers
- G) Help to reduce the scars and cavity formation
- H) Improve the regeneration of nerve fibers and also functional recovery

Scaffold implants (between 3-10 vertebrae) are performed either immediately after the creation of the lesion or after a period of time has passed since the creation of the lesion; in the second case, due to the production of glial scars, the repair of the SCI faces a problem. Different synthetic and natural polymers are used to prepare 3D scaffolds. Scaffolds prepared with natural polymers compared to scaffolds prepared with synthetic polymers (I) improve the adhesion ability of implanted cells, (II) have good biocompatibility and degradation, (III) non-toxic, (IV) increase the survival time of implanted cells inside the body, (V) increase the rate of differentiation of implanted cells into nerve cells, and (VI) improve tissue regeneration and functional rehabilitation.

The use of loaded growth factors in scaffolds is another solution for SCI treatment. The implant of these scaffolds in the lesion site and the gradual release of growth factors are significantly effective in neuron regeneration and subsequent functional recovery. In addition, growth factors help to decrease cavity and glial scar formation. 3D scaffolds containing cells compared to scaffolds without cells and scaffolds containing growth factors notably improve neuron regeneration and motor functional recovery. The degree of stiffness of the scaffolds, which can be adjusted by changing the concentration of the components in bioink, is effective in the differentiation of NSCs into neurons or astrocytes. In this case, if the amount of elastic modulus is less than 1 kPa, the NSCs cells become neurons, and if it is 3 kPa or more, an obvious reduction of differentiated neurons occurs. Cell grafts can rarely viable for a long time because of the presence of inflammatory and toxic blood products at the injury site, however the cells loaded in the 3D scaffolds survive at the site of the lesion for more than 12 weeks and

differentiated to neurons and oligodendrocytes, while cells without scaffolds barely survived for 4 weeks. The NSCs cells loaded in the scaffold can differentiate into functional neurons related to movement and sensation, which ultimately improves functional recovery. According to research results, axon regeneration alone is not enough to restore motor functions, and in the regeneration process, another key factor is remyelination of regenerated axons. In this regards, the simultaneous use of two types of cells, NSCs and OLGs, in combination with 3D printing scaffolds has been beneficial in promoting remyelination and improving the therapeutic effect of SCI. While 3D printed scaffolds containing cells help in neurological regeneration, as well as protected the rat from hard urinary tract complications caused by SCI. In addition, the prepared scaffolds are safe for other organs like as lungs, liver, spleen and heart. According to the results of various studies to improve the efficiency of 3D printed scaffolds containing cells in SCI repair as well as their use in the clinical phase in the near future, the following are suggested.

1- In clinical application, using polymers with complex structure and variable components such as matrigel has a limitation and for this reason it is better replacing it with other polymers such as laminin and collagen type 4.

2- Simultaneous use of two or more cells and growth factors in order to better and faster reconstruction of SCI.

Authors' Contribution

Conceptualization: Salar Khaledian, Reza Fatahian

Investigation: Ghobad Mohammadi, Mohadese Abdoli, Arad Fatahian, Arya Fatahian

Project administration: Salar Khaledian, Reza Fatahian.

Supervision: Reza Fatahian.

Validation: Salar Khaledian, Reza Fatahian, Ghobad Mohammadi, Mohadese Abdoli, Arad Fatahian, Arya Fatahian.

Visualization: Salar Khaledian, Reza Fatahian, Ghobad Mohammadi, Mohadese Abdoli, Arad Fatahian, Arya Fatahian.

Writing—original draft: Salar Khaledian, Reza Fatahian.

Writing—review & editing: Salar Khaledian, Reza Fatahian.

Competing interest

The authors declare that they have no known competing financial interests or personal relationships that could have appeared to influence the work reported in this paper.

Ethical Approval

Not applicable.

Funding

This research did not receive any specific grant from funding agencies in the public, commercial, or not-for-profit sectors.

References

1. Vijayavenkataraman S, Shuo Z, Fuh JY, Lu WF. Design of three-dimensional scaffolds with tunable matrix stiffness for directing stem cell lineage specification: An in silico study. *Bioeng* 2017;4(3):66. doi: 10.3390/bioengineering4030066
2. Jammalamadaka U, Tappa K. Recent advances in biomaterials for 3D printing and tissue engineering. *J Funct Biomater* 2018;9(1):22. doi: 10.3390/jfb9010022
3. Ambekar RS, Kandasubramanian B. Progress in the advancement of porous biopolymer scaffold: tissue engineering application. *Ind Eng Chem Res* 2019;58(16):6163-94. doi: 10.1021/acs.iecr.8b05334
4. Asadi N, Del Bakhshayesh AR, Davaran S, Akbarzadeh A. Common biocompatible polymeric materials for tissue engineering and regenerative medicine. *Mater Chem Phys* 2020;242:122528. doi: 10.1016/j.matchemphys.2019.122528
5. Maji K, Dasgupta S, Pramanik K, Bissoyi A. Preparation and evaluation of gelatin-chitosan-nanobioglass 3D porous scaffold for bone tissue engineering. *Int J Biomater* 2016;2016:9825659. doi: 10.1155/2016/9825659
6. Boni R, Ali A, Shavandi A, Clarkson AN. Current and novel polymeric biomaterials for neural tissue engineering. *J Biomed Sci* 2018;25(1):90. doi: 10.1186/s12929-018-0491-8
7. Koffler J, Zhu W, Qu X, Platoshyn O, Dulin JN, Brock J, et al. Biomimetic 3D-printed scaffolds for spinal cord injury repair. *Nat Med* 2019;25(2):263-9. doi: 10.1038/s41591-018-0296-z
8. Venkatesh K, Ghosh SK, Mullick M, Manivasagam G, Sen D. Spinal cord injury: pathophysiology, treatment strategies, associated challenges, and future implications. *Cell Tissue Res* 2019;377:125-51. doi: 10.1007/s00441-019-03039-1
9. Kapalczyńska M, Kolenda T, Przybyła W, Zajączkowska M, Teresiak A, Filas V, et al. 2D and 3D cell cultures—a comparison of different types of cancer cell cultures. *AMS* 2018;14(4):910-9. doi: <https://doi.org/10.5114/aoms.2016.63743>
10. Dutta RC, Dutta AK. Cell-interactive 3D-scaffold; advances and applications. *Biotechnol Adv* 2009;27(4):334-9. doi: 10.1016/j.biotechadv.2009.02.002
11. Sun Y, Yang C, Zhu X, Wang JJ, Liu XY, Yang XP, et al. 3D printing collagen/chitosan scaffold ameliorated axon regeneration and neurological recovery after spinal cord injury. *J Biomed Mater Res A* 2019;107(9):1898-908. doi: 10.1002/jbm.a.36675
12. Do AV, Khorsand B, Geary SM, Salem AK. 3D printing of scaffolds for tissue regeneration applications. *Adv Healthc Mater* 2015;4(12):1742-62. doi: 10.1002/adhm.201500168
13. Zhang L, Yang G, Johnson BN, Jia X. Three-dimensional (3D) printed scaffold and material selection for bone repair. *Acta Biomater* 2019;84:16-33. doi: 10.1016/j.actbio.2018.11.039
14. Williams DF. On the mechanisms of biocompatibility. *Biomater* 2008;29(20):2941-53. doi: 10.1016/j.biomaterials.2008.04.023
15. Salgado AJ, Coutinho OP, Reis RL. Bone tissue engineering: state of the art and future trends. *Macromol Biosci* 2004;4(8):743-65. doi: 10.1002/mabi.200400026
16. Karageorgiou V, Kaplan D. Porosity of 3D biomaterial scaffolds and osteogenesis. *Biomater* 2005;26(27):5474-91. doi: 10.1016/j.biomaterials.2005.02.002
17. Sanzana ES, Navarro M, Ginebra MP, Planell JA, Ojeda AC, Montecinos HA. Role of porosity and pore architecture in the in vivo bone regeneration capacity of biodegradable glass scaffolds. *J Biomed Mater Res A* 2014;102(6):1767-73. doi: 10.1002/jbm.a.34845
18. Ebrahimi M. Porosity parameters in biomaterial science: definition, impact, and challenges in tissue engineering. *Front Mater Sci* 2021;15(3):352-73. doi: <https://doi.org/10.1007/s11706-021-0558-4>
19. Beniwal G, Saxena KK. A review on pore and porosity in tissue engineering. *Mater Today: Proc* 2021;44:2623-8. doi: <https://doi.org/10.1016/j.matpr.2020.12.661>

20. Liu X-Y, Chen C, Xu H-H, Zhang Y-s, Zhong L, Hu N, et al. Integrated printed BDNF/collagen/chitosan scaffolds with low temperature extrusion 3D printer accelerated neural regeneration after spinal cord injury. *Regen Biomater* 2021;8(6):rbab047. doi: <https://doi.org/10.1093/rb/rbab047>
21. Gao C, Li Y, Liu X, Huang J, Zhang Z. 3D bioprinted conductive spinal cord biomimetic scaffolds for promoting neuronal differentiation of neural stem cells and repairing of spinal cord injury. *Chem Eng J* 2023;451:138788. doi: 10.1016/j.cej.2022.138788
22. Carver WE. 19 CHAPTER The Extracellular Matrix. *Medical Biochemistry-E-Book* 2022:255.
23. Huang X, Zhang Y, Zheng X, Yu G, Dan N, Dan W, et al. Origin of critical nature and stability enhancement in collagen matrix based biomaterials: Comprehensive modification technologies. *Int J Biol Macromol* 2022;216:741-56. doi: 10.1016/j.ijbiomac.2022.07.199
24. Rainey JK, Goh MC. A statistically derived parameterization for the collagen triple-helix. *Protein Sci* 2002;11(11):2748-54. doi: 10.1110/ps.0218502
25. Xu Y, Zhang F, Zhai W, Cheng S, Li J, Wang Y. Unraveling of advances in 3D-printed polymer-based bone scaffolds. *Polym* 2022;14(3):566. doi: <https://doi.org/10.3390/polym14030566>
26. Liu T, Houle JD, Xu J, Chan BP, Chew SY. Nanofibrous collagen nerve conduits for spinal cord repair. *Tissue Eng Part A* 2012;18(9-10):1057-66. doi: 10.1089/ten.TEA.2011.0430
27. Wang N, Xiao Z, Zhao Y, Wang B, Li X, Li J, et al. Collagen scaffold combined with human umbilical cord-derived mesenchymal stem cells promote functional recovery after scar resection in rats with chronic spinal cord injury. *J Tissue Eng Regen Med* 2018;12(2):e1154-e63. doi: 10.1002/term.2450
28. Deng W-S, Ma K, Liang B, Liu X-Y, Xu H-Y, Zhang J, et al. Collagen scaffold combined with human umbilical cord-mesenchymal stem cells transplantation for acute complete spinal cord injury. *Neural Regen Res* 2020;15(9):1686. doi: 10.4103/1673-5374.276340
29. Garvin J, Qi J, Maloney M, Banes AJ. Novel system for engineering bioartificial tendons and application of mechanical load. *Tissue Eng* 2003;9(5):967-79. doi: 10.1089/107632703322495619
30. He X, Li W, Liu S, Li Y, Chen Y, Dan N, et al. Fabrication of high-strength, flexible, porous collagen-based scaffolds to promote tissue regeneration. *Materials Today Bio* 2022;16:100376. doi: <https://doi.org/10.1016/j.mtbio.2022.100376>
31. Li J, Ren N, Qiu J, Jiang H, Zhao H, Wang G, et al. Carbodiimide crosslinked collagen from porcine dermal matrix for high-strength tissue engineering scaffold. *Int J Biol Macromol* 2013;61:69-74. doi: <https://doi.org/10.1016/j.ijbiomac.2013.06.038>
32. Štiglic AD, Lackner F, Nagaraj C, Beaumont M, Bračič M, Duarte I, et al. 3D-Printed Collagen–Nanocellulose Hybrid Bioscaffolds with Tailored Properties for Tissue Engineering Applications. *ACS Appl Bio Mater* 2023;6(12):5596. doi: <https://doi.org/10.1021%2Facsabm.3c00767>
33. Santos VP, Marques NS, Maia PC, Lima MABd, Franco LdO, Campos-Takaki GMd. Seafood waste as attractive source of chitin and chitosan production and their applications. *Int J Mol Sci* 2020;21(12):4290. doi: <http://dx.doi.org/10.3390/ijms21124290>
34. Group EBCTC. Effects of chemotherapy and hormonal therapy for early breast cancer on recurrence and 15-year survival: an overview of the randomised trials. *Lancet* 2005;365(9472):1687-717. doi: [https://doi.org/10.1016/S0140-6736\(05\)66544-0](https://doi.org/10.1016/S0140-6736(05)66544-0)
35. Rao SB, Sharma CP. Use of chitosan as a biomaterial: studies on its safety and hemostatic potential. *J Biomed Mater Res* 1997;34(1):21-8.
36. Elizalde-Peña E, Quintero-Ortega I, Zárate-Triviño D, Nuño-Licona A, Gough J, Sanchez I, et al. (Chitosan-g-glycidyl methacrylate)-xanthan hydrogel implant in Wistar rats for spinal

- cord regeneration. *Mater Sci Eng C* 2017;78:892-900. doi: <https://doi.org/10.1016/j.msec.2017.03.005>
37. Yao Z-a, Chen F-j, Cui H-l, Lin T, Guo N, Wu H-g. Efficacy of chitosan and sodium alginate scaffolds for repair of spinal cord injury in rats. *Neural Regen Res* 2018;13(3):502. doi: 10.4103/1673-5374.228756
 38. Prang P, Müller R, Eljaouhari A, Heckmann K, Kunz W, Weber T, et al. The promotion of oriented axonal regrowth in the injured spinal cord by alginate-based anisotropic capillary hydrogels. *Biomater* 2006;27(19):3560-9. doi: 10.1016/j.biomaterials.2006.01.053
 39. Lee KY, Mooney DJ. Alginate: properties and biomedical applications. *Prog Polym Sci* 2012;37(1):106-26. doi: 10.1016/j.progpolymsci.2011.06.003
 40. Günther MI, Weidner N, Müller R, Blesch A. Cell-seeded alginate hydrogel scaffolds promote directed linear axonal regeneration in the injured rat spinal cord. *Acta Biomater* 2015;27:140-50. doi: <https://doi.org/10.1016/j.actbio.2015.09.001>
 41. Nawaz S, Khan S, Farooq U, Haider MS, Ranjha NM, Rasul A, et al. Biocompatible hydrogels for the controlled delivery of anti-hypertensive agent: Development, characterization and in vitro evaluation. *Des Monomers Polym* 2018;21(1):18-32. doi: <https://doi.org/10.1080/15685551.2018.1445416>
 42. Sakai S, Hirose K, Taguchi K, Ogushi Y, Kawakami K. An injectable, in situ enzymatically gellable, gelatin derivative for drug delivery and tissue engineering. *Biomater* 2009;30(20):3371-7. doi: 10.1016/j.biomaterials.2009.03.030
 43. Lukin I, Erezuma I, Maeso L, Zarate J, Desimone MF, Al-Tel TH, et al. Progress in gelatin as biomaterial for tissue engineering. *Pharm* 2022;14(6):1177. doi: <https://doi.org/10.3390/pharmaceutics14061177>
 44. Liu S, Yang H, Chen D, Xie Y, Tai C, Wang L, et al. Three-dimensional bioprinting sodium alginate/gelatin scaffold combined with neural stem cells and oligodendrocytes markedly promoting nerve regeneration after spinal cord injury. *Regen Biomater* 2022;9:rbac038. doi: 10.1093/rb/rbac038
 45. Wenk E, Merkle HP, Meinel L. Silk fibroin as a vehicle for drug delivery applications. *J Control Release* 2011;150(2):128-41. doi: <https://doi.org/10.1016/j.jconrel.2010.11.007>
 46. Ayoub NA, Garb JE, Tinghitella RM, Collin MA, Hayashi CY. Blueprint for a high-performance biomaterial: full-length spider dragline silk genes. *PLoS One* 2007;2(6):e514. doi: 10.1371/journal.pone.0000514
 47. Kundu B, Rajkhowa R, Kundu SC, Wang X. Silk fibroin biomaterials for tissue regenerations. *Adv Drug Deliv Rev* 2013;65(4):457-70. doi: 10.1016/j.addr.2012.09.043
 48. Sun K, Li H, Li R, Nian Z, Li D, Xu C. Silk fibroin/collagen and silk fibroin/chitosan blended three-dimensional scaffolds for tissue engineering. *Eur J Orthop Surg Traumatol* 2015;25(2):243-9. doi: 10.1007/s00590-014-1515-z
 49. Chen C, Xu H-H, Liu X-Y, Zhang Y-S, Zhong L, Wang Y-W, et al. 3D printed collagen/silk fibroin scaffolds carrying the secretome of human umbilical mesenchymal stem cells ameliorated neurological dysfunction after spinal cord injury in rats. *Regen Biomater* 2022;9:rbac014. doi: 10.1093/rb/rbac014
 50. Li X-H, Zhu X, Liu X-Y, Xu H-H, Jiang W, Wang J-J, et al. The corticospinal tract structure of collagen/silk fibroin scaffold implants using 3D printing promotes functional recovery after complete spinal cord transection in rats. *J Mater Sci Mater Med* 2021;32(4):1-13. doi: 10.1007/s10856-021-06500-2
 51. Kleinman HK, Martin GR, editors. Matrigel: basement membrane matrix with biological activity. Seminars in cancer biology; 2005: Elsevier.
 52. Kleinman HK, McGarvey ML, Liotta LA, Robey PG, Tryggvason K, Martin GR. Isolation and characterization of type IV procollagen, laminin, and heparan sulfate proteoglycan from the EHS sarcoma. *Biochem* 1982;21(24):6188-93. doi: 10.1021/bi00267a025

53. Orkin R, Gehron P, McGoodwin E, Martin G, Valentine T, Swarm R. A murine tumor producing a matrix of basement membrane. *J Exp Med* 1977;145(1):204-20. doi: 10.1084/jem.145.1.204
54. Morritt AN, Bortolotto SK, Dilley RJ, Han X, Kompa AR, McCombe D, et al. Cardiac tissue engineering in an in vivo vascularized chamber. *Circ* 2007;115(3):353-60. doi: 10.1161/CIRCULATIONAHA.106.657379
55. Ponce ML. Tube formation: an in vitro matrigel angiogenesis assay. *Angiogenesis protocols*: Springer; 2009. p. 183-8.
56. Lu Y-C, Song W, An D, Kim BJ, Schwartz R, Wu M, et al. Designing compartmentalized hydrogel microparticles for cell encapsulation and scalable 3D cell culture. *J Mater Chem B* 2015;3(3):353-60. doi: 10.1039/c4tb01735h
57. Tibbitt MW, Anseth KS. Hydrogels as extracellular matrix mimics for 3D cell culture. *Biotechnol Bioeng* 2009;103(4):655-63. doi: 10.1002/bit.22361
58. Li Y, Cao X, Deng W, Yu Q, Sun C, Ma P, et al. 3D printable Sodium alginate-Matrigel (SA-MA) hydrogel facilitated ectomesenchymal stem cells (EMSCs) neuron differentiation. *J Biomater Appl* 2021;35(6):709-19. doi: 10.1177/0885328220961261
59. Abatangelo G, Vindigni V, Avruscio G, Pandis L, Brun P. Hyaluronic Acid: Redefining Its Role. *Cells* 2020;9(7):1743. doi: 10.3390/cells9071743
60. Collins MN, Birkinshaw C. Hyaluronic acid based scaffolds for tissue engineering—A review. *Carbohydr Polym* 2013;92(2):1262-79. doi: <https://doi.org/10.1016/j.carbpol.2012.10.028>
61. Zhu J, Marchant RE. Design properties of hydrogel tissue-engineering scaffolds. *Expert Rev Med Devices* 2011;8(5):607-26. doi: 10.1586/erd.11.27
62. Burdick JA, Prestwich GD. Hyaluronic acid hydrogels for biomedical applications. *Adv Mater*, 2011;23(12):H41-H56. doi: 10.1002/adma.201003963
63. Ilhan E, Cesur S, Guler E, Topal F, Albayrak D, Guncu MM, et al. Development of Satureja cuneifolia-loaded sodium alginate/polyethylene glycol scaffolds produced by 3D-printing technology as a diabetic wound dressing material. *Int J Biol Macromol* 2020;161:1040-54. doi: <https://doi.org/10.1016/j.ijbiomac.2020.06.086>
64. De-Paula MMM, Afewerki S, Viana BC, Webster TJ, Lobo AO, Marciano FR. Dual effective core-shell electrospun scaffolds: Promoting osteoblast maturation and reducing bacteria activity. *Mater Sci Eng C* 2019;103:109778. doi: 10.1016/j.msec.2019.109778
65. Shi R. Polyethylene glycol repairs membrane damage and enhances functional recovery: a tissue engineering approach to spinal cord injury. *Neurosci Bull* 2013;29(4):460-6. doi: 10.1007/s12264-013-1364-5
66. Unagolla JM, Jayasuriya AC. Hydrogel-based 3D bioprinting: A comprehensive review on cell-laden hydrogels, bioink formulations, and future perspectives. *Appl Mater Today* 2020;18:100479. doi: <https://doi.org/10.1016/j.apmt.2019.100479>
67. Knowlton S, Anand S, Shah T, Tasoglu S. Bioprinting for neural tissue engineering. *Trends Neurosci* 2018;41(1):31-46. doi: 10.1016/j.tins.2017.11.001
68. Zhuang P, Sun AX, An J, Chua CK, Chew SY. 3D neural tissue models: From spheroids to bioprinting. *Biomater* 2018;154:113-33. doi: 10.1016/j.biomaterials.2017.10.002
69. Matai I, Kaur G, Seyedsalehi A, McClinton A, Laurencin CT. Progress in 3D bioprinting technology for tissue/organ regenerative engineering. *Biomater* 2020;226:119536. doi: 10.1016/j.biomaterials.2019.119536
70. Yu J, Park SA, Kim WD, Ha T, Xin Y-Z, Lee J, et al. Current advances in 3D bioprinting technology and its applications for tissue engineering. *Polym* 2020;12(12):2958. doi: 10.3390/polym12122958
71. Panwar A, Tan LP. Current status of bioinks for micro-extrusion-based 3D bioprinting. *Mol* 2016;21(6):685. doi: 10.3390/molecules21060685

72. Murphy SV, Atala A. 3D bioprinting of tissues and organs. *Nat Biotechnol* 2014;32(8):773-85. doi: 10.1038/nbt.2958
73. O'Brien CM, Holmes B, Faucett S, Zhang LG. Three-dimensional printing of nanomaterial scaffolds for complex tissue regeneration. *Tissue Eng Part B Rev* 2015;21(1):103-14. doi: 10.1089/ten.TEB.2014.0168
74. Hospodiuk M, Dey M, Sosnoski D, Ozbolat IT. The bioink: A comprehensive review on bioprintable materials. *Biotechnol Adv* 2017;35(2):217-39. doi: 10.1016/j.biotechadv.2016.12.006
75. Bishop ES, Mostafa S, Pakvasa M, Luu HH, Lee MJ, Wolf JM, et al. 3-D bioprinting technologies in tissue engineering and regenerative medicine: Current and future trends. *Genes Dis* 2017;4(4):185-95. doi: 10.1016/j.gendis.2017.10.002
76. Derakhshanfar S, Mbeleck R, Xu K, Zhang X, Zhong W, Xing M. 3D bioprinting for biomedical devices and tissue engineering: A review of recent trends and advances. *Bioact Mater* 2018;3(2):144-56. doi: 10.1016/j.bioactmat.2017.11.008
77. Davoodi E, Sarikhani E, Montazerian H, Ahadian S, Costantini M, Swieszkowski W, et al. Extrusion and microfluidic-based bioprinting to fabricate biomimetic tissues and organs. *Adv Mater Technol* 2020;5(8):1901044. doi: 10.1002/admt.201901044
78. Nair K, Gandhi M, Khalil S, Yan KC, Marcolongo M, Barbee K, et al. Characterization of cell viability during bioprinting processes. *Biotechnol J* 2009;4(8):1168-77. doi: 10.1002/biot.200900004
79. Chang CC, Boland ED, Williams SK, Hoying JB. Direct-write bioprinting three-dimensional biohybrid systems for future regenerative therapies. *J Biomed Mater Res Part B Appl Biomater* 2011;98(1):160-70. doi: 10.1002/jbm.b.31831
80. Cui X, Dean D, Ruggeri ZM, Boland T. Cell damage evaluation of thermal inkjet printed Chinese hamster ovary cells. *Biotechnol Bioeng* 2010;106(6):963-9. doi: 10.1002/bit.22762
81. Cui X, Boland T, DD'Lima D, K Lotz M. Thermal inkjet printing in tissue engineering and regenerative medicine. *Recent Pat Drug Deliv Formul* 2012;6(2):149-55. doi: 10.2174/187221112800672949
82. Ventura RD. An overview of laser-assisted bioprinting (LAB) in tissue engineering applications. *Lasers Med Sci* 2021;10(2):76-81.
83. Gruene M, Deiwick A, Koch L, Schlie S, Unger C, Hofmann N, et al. Laser printing of stem cells for biofabrication of scaffold-free autologous grafts. *Tissue Eng Part C Methods* 2011;17(1):79-87. doi: 10.1089/ten.TEC.2010.0359
84. Koch L, Kuhn S, Sorg H, Gruene M, Schlie S, Gaebel R, et al. Laser printing of skin cells and human stem cells. *Tissue Eng Part C Methods* 2010;16(5):847-54. doi: 10.1089/ten.TEC.2009.0397
85. Hopp B, Smausz T, Kresz N, Barna N, Bor Z, Kolozsvári L, et al. Survival and proliferative ability of various living cell types after laser-induced forward transfer. *Tissue Eng* 2005;11(11-12):1817-23.
86. Guillotin B, Souquet A, Catros S, Duocastella M, Pippenger B, Bellance S, et al. Laser assisted bioprinting of engineered tissue with high cell density and microscale organization. *Biomater* 2010;31(28):7250-6. doi: 10.1016/j.biomaterials.2010.05.055
87. Ligon SC, Liska R, Stampfl J, Gurr M, Mülhaupt R. Polymers for 3D printing and customized additive manufacturing. *Chem Rev* 2017;117(15):10212-90. doi: 10.1021/acs.chemrev.7b00074
88. Melchels FP, Feijen J, Grijpma DW. A review on stereolithography and its applications in biomedical engineering. *Biomater* 2010;31(24):6121-30. doi: 10.1016/j.biomaterials.2010.04.050

89. Choi JS, Kang H-W, Lee IH, Ko TJ, Cho D-W. Development of micro-stereolithography technology using a UV lamp and optical fiber. *Int J Adv Manuf Technol* 2009;41:281-6. doi: <https://doi.org/10.1007/s00170-008-1461-1>
90. Skoog SA, Goering PL, Narayan RJ. Stereolithography in tissue engineering. *J Mater Sci Mater Med* 2014;25(3):845-56. doi: 10.1007/s10856-013-5107-y
91. Russo FB, Freitas BC, Pignatari GC, Fernandes IR, Sebat J, Muotri AR, et al. Modeling the interplay between neurons and astrocytes in autism using human induced pluripotent stem cells. *Biol Psychiatry* 2018;83(7):569-78. doi: <https://doi.org/10.1016/j.biopsych.2017.09.021>
92. Tran KA. Bioengineered Scaffolds to Induce Alignment and Promote Axon Regeneration following Spinal Cord Injury: Rowan University; 2022.
93. Chawla K, Yu TB, Liao SW, Guan Z. Biodegradable and biocompatible synthetic saccharide-peptide hydrogels for three-dimensional stem cell culture. *Biomacromolecules* 2011;12(3):560-7. doi: 10.1021/bm100980w
94. Yang J, Yang K, Man W, Zheng J, Cao Z, Yang C-Y, et al. 3D bio-printed living nerve-like fibers refine the ecological niche for long-distance spinal cord injury regeneration. *Bioact Mater* 2023;25:160-75. doi: 10.1016/j.bioactmat.2023.01.023
95. Joung D, Truong V, Neitzke CC, Guo SZ, Walsh PJ, Monat JR, et al. 3D printed stem-cell derived neural progenitors generate spinal cord scaffolds. *Adv Funct Mater* 2018;28(39):1801850. doi: 10.1002/adfm.201801850
96. Liu X, Hao M, Chen Z, Zhang T, Huang J, Dai J, et al. 3D bioprinted neural tissue constructs for spinal cord injury repair. *Biomater* 2021;272:120771. doi: 10.1016/j.biomaterials.2021.120771
97. Jiang J-P, Liu X-Y, Zhao F, Zhu X, Li X-Y, Niu X-G, et al. Three-dimensional bioprinting collagen/silk fibroin scaffold combined with neural stem cells promotes nerve regeneration after spinal cord injury. *Neural Regen Res* 2020;15(5):959. doi: 10.4103/1673-5374.268974
98. Brusko GD, Cox EM, Wang MY. 3-Dimensional Printing a Novel Framework for Spinal Cord Injury Repair. *Neurosurg* 2019;85(2):E192-E3. doi: 10.1093/neuros/nyz169